

Evaluation of the Absorbance and Transmittance of the Optical Light for Three Different Types of Composite Resin Stored in Artificial Saliva (in vitro study)

Rajaa T. Suliman
BDS, MSc (Lect)

Department of Conservative Dentistry
College of Dentistry, University of Mosul

الخلاصة

الأهداف: لتقييم الإمتصاص وقابلية النقل للضوء البصري لثلاثة أنواع مختلفة لمكون راتنج الأسنان المخزون في اللعاب الصناعي. **المواد وطرائق العمل:** ٣٠ عينة تم تحضيرها من الراتنج المفعل ضوئياً تم تقسيمها إلى ثلاث مجاميع. المجموعة الأولى: ١٠ عينات تم تحضيرها من الـ Els **المجموعة الثانية:** ١٠ عينات من الـ Tetric n ceram **المجموعة الثالثة:** ١٠ عينات من الـ Solitaire 2. تم قياس الإمتصاص باستخدام المطياف الضوئي. حيث أستغرق تقييم العينات بعد مرور (صفر و ١ و ٧ و ٢٨) أيام مستمرة مخزونة في لعاب صناعي. **النتائج:** التحليل الإحصائي أظهر إختلاف ملحوظ ومهم ($P \leq 0.05$) بين المجاميع المختبرة وبنفس الوقت المستغرق بالغمر، أظهر الـ Solitaire 2 طرق إمتصاص أعلى بالمقارنة مع الـ Tetric و الـ Els خاصة بعد مرور يوم واحد غمر في اللعاب الصناعي، ولم يكن أي إختلاف ذو دلالة مهمة $P > 0.05$ بأوقات الغمر المختلفة في اللعاب ضمن المجموعة الواحدة، ويظهر الـ Els نسبة إمتصاص أقل ونقل أعلى $T\%$ مما هو عليه في مكون الراتنج Tetric و Solitaire 2. **الإستنتاجات:** أظهر التحليل الإحصائي ان حشوة الراتنج منقبض البلمرة المنخفضة الـ Els أقل إمتصاص وأعلى نسبة نقل للضوء البصري، ويظهر Poly glass أعلى إمتصاص وأقل نسبة نقل للضوء مقارنة مع الـ Tetric و الـ Els. وأيضاً أداء المجاميع لا يختلف إحصائياً من حيث الوقت المستغرق في الغمر باللعاب الصناعي

ABSTRACT

Aims: To evaluate the Absorbance and transmittance of the optical light for three different types of light activated dental composite resin stored in artificial saliva. **Materials and Methods:** 30 specimens were prepared from light activated composite resin and divided in to three groups, G1: 10 specimens prepared from Els, G2: 10 specimens prepared from Tetric n Ceram, G3: 10 specimens prepared from Solitaire2. Absorbance of the optical light measured using spectrophotometer. The specimens were evaluated after (zero,1,7,28) day immersion time in artificial saliva. **Results:** Statistical analysis shows significant difference at $P \leq 0.05$ among tested groups at same immersion time, Solitaire 2 showed highest absorbance means compare to Tetric, Els specially after 1 day immersion in artificial saliva. No significant difference $P > 0.05$ in absorbance mean at various immersion time in artificial saliva for each group. Els shows low absorbance and highest transmittance percentage $T\%$ than Tetric and Solitaire composite resin. **Conclusion:** The Els extra composite resin has lowest absorbance and highest transmittance means for optical light, Solitaire2 showed more absorbance means with less amount of light transmittance through the composite resin compare to Tetric and Els. The performance of the experimented groups statistically not significant in terms of immersion time in artificial saliva.

Key words: Absorbance, Transmittance, composite resin, artificial saliva spectrophotometer.

Suliman RT. Evaluation of the Absorbance and Transmittance of the Optical Light for Three Different Types of Composite Resin Stored in Artificial Saliva (in vitro study). *Al-Rafidain Dent J.* 2017(1):86-97.

Received: 20/3/2014 **Sent to Referees:** 3/4/2014 **Accepted for Publication:** 13/5/2014

INTRODUCTION

Composite resin is a heterogeneous material that is composed of three major component (resin matrix, filler particles and saline coupling agent. Since 1960 dental

composite has undergone a lot of changes in order to become a restorative material with acceptable aesthetic properties, recent advancement in direct dental restorative materials is the incorporation of the

nanotechnology which is understanding and control mater at dimension of roughly 1-100nm, also new dental composite formulation reinforced by nano and micro filler dental restorative materials which include nanometric and micrometric inorganic particles as reinforcing fillers⁽¹⁾.

In recent years resin composite have been used extensively as an alternative to dental amalgam, With this increase in the use has come, the desire to improve the various properties (absorbance, optical, physical mechanical) properties for resin composite⁽²⁾. In general, dental composite and other restorative filling materials used in dentistry are required to have long term durability in the oral cavity were the filling materials is in contact with saliva fluid, that contains a variety of inorganic species together with bacterial flora complex^(2,3).

Despite the substantial advances in direct esthetic filling materials, particularly light cured composite resins these materials still possess a number of properties that interface in their clinical performance such as compressive strength, hardness, abrasive strength, polymerization shrinkage, homogenization, translucence, absorbance for optical light superficial staining, elasticity modulus, and coefficient of liner thermal expansion, the inadequacy of these properties can cause a negative performance of a restoration with color instability resulting from superficial staining and

internal discoloration among other faults⁽⁴⁾.

Several factors can affect the esthetic result of the restoration with composite resin in anterior teeth, most of these factors involve the esthetic limitations of the filling material, such as absorbance which according to several authors can be modified by water absorption chemical degradation and micro fractures. Light cured composite resin are less absorbance and more transmittance than chemical cure activated resin because the former are less pigmented over all a reduction in transmittance is observed over time^(5,6). However few studies have focused specifically on determining the absorbance of the optical light for composite resin materials which are so important for the esthetic success of a restoration⁽⁵⁾. Optical properties of composite restorative materials both cured and uncured are obvious important in a procedure of reliant on photo activation since they may affect light transmittance and therefore materials conversion upon which effect on mechanical properties and ultimate clinical performance of composite⁽⁷⁾. The aim of this study was to evaluate the absorbance and transmittance of the optical light for three different types of light activated composite resin (Els extra, Tetric n ceram, Solitaire 2 composite resin) after zero, 1, 7, 28 days storage in artificial saliva using UV light spectrophotometer.

MATERIALS AND METHODS

The study was carried out in the department of conservative dentistry and dental basic science. A total of 30 specimens (bar) in shapes, 30 mm in length, 10mm in width, less than 1mm in thickness (0.5mm) were prepared from three different types of light activated composite resin, composition as shown in Table (1). Group1: 10 specimens were prepared from light activated microhybrid Els extra (Saremco Dental), Group2: 10 specimens were prepared from light activated nanohybrid composite resin Tetric-n ceram (Ivoclar Vivadent liechstenein), Group3: 10 specimens were prepared from light activated poly glass composite resin Solitaire 2 (Heraeus Kulzer Germany).

The specimens were prepared in plastic mold (30 mm in length, 10 mm in


width and less than 1mm in thickness (0.5mm) standardization measurement using digital vernier caliper (made in Germany).

The composite resins were packed in the mold using an incremental technique with a plastic instrument (then adapted as one layer), glass slide and celluloid strip were placed on the top and bottom of the mold to provide flat surface as shown in Figure (1), and facilitate light curing the specimens were cured with visible light cured (activation) was done with Blue-luxcer TM curing light (Model M 855 Halogen lamp monitex Taiwan 08H0151) for 40 seconds, with light tip was placed in contact with the glass slide (with exception of the thickness of glass slide and celluloid strip at a distance of 1.0mm from the specimens) from the top of the specimens.

Table(1): Compositions of three different types of light activated composite resin.

Composite resin	Composition	Particle size distribution.	Manufacture
Els extra	Barium glass, silanized, Bis-GMA, Bis-EMA, catalyst, inhibitors, and pigments.	0.1- 2.8µm highly filled	Saremco Dental Switzerland
Tetric n – Ceram	Dimethacrylates (19-20 wt%) barium glass, ytterbium trifluoride, mixed oxide, copolymers (80-81 wt%), catalyysts, stabilizers and pigments (<1 wt%) inorganic filler 55–57 vol %	40 nm – 3000 nm	Ivoclar Vivadent
Solitaire 2	Multicross – linking urethane (meth) acrylate monomers, BaAF – silicate glass, Porous silicon dioxide	0.02 - 23 µm ϕ 0.7 µm; max < 2µm ϕ 8 µm; max < 23µm	Heraeus – kulzer

Bis-GMA: Bisphenol Adiglycidyl methacrylate, Bis EMA: Bisphenol Apolyethylene glycol diether dimethacrylate. ϕ : mean percentage

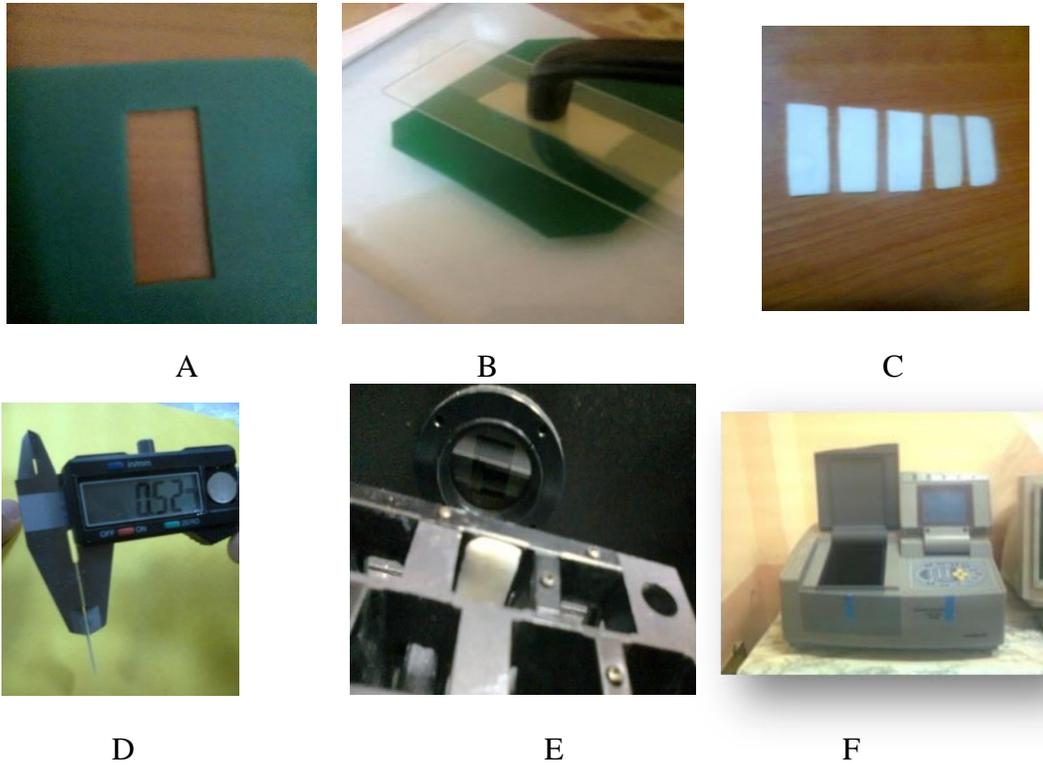

Figure(1): Preparation of composite resin specimens

- A: mold
- B: Specimens in the mold
- C: Specimens (composite resin bars)
- D: Digital vernier caliper
- E: Specimens under examination
- F: Spectrophotometer

Light cure for the specimens through the glass slides and celluloid strip was exposed to light from upper, lower, right, left cover strip sides with light intensity of the curing light unit was standardized to at least 500nm(output),double the recommended time to ensure complete polymerization of the specimens which removed from the molds^(4,5,6,8).

The resin bars were finished and polished to a uniform surface using carbide bur (Komet, UK) at medium speed for 10 second under water coolant for each of the surface to

create base line finishing and polishing procedure include using (Sof -Lex) polishing system which include using multistep abrasive disc (Sof -Lex)TM aluminum oxide disk Sof-Lex (3M ESPE Dental products St. paul. USA) used for polishing composite bars^(6,8), surface finishing and polishing attributed to the removal of the surface layer of resin rich inorganic matter and the staining susceptibility of composite resin depend on its composition and surface properties, the susceptible to staining showed that the

lowest staining was generally correlated with lowest water absorption, low organic matrix content and satisfactory brightness after finishing and polishing, the composite bars washed in distilled water and dried with air syringe before taking the reading⁽⁶⁾.

Absorbance values for the composite resin bar measured using an ultra-violet visible spectrophotometer (UV-UIS Dual 8 Auto CEIL CE UVS-2800 LABO MED Inc, UK)^(6,9). At wave length (245)nm through direct transmission absorbance was measured immediately after preparation of the bars (finishing and polishing) at zero

time before immersion in artificial saliva. The other measurements for the bars were taken after (1,7,28) days immersion in artificial saliva (chemical compositions)⁽³⁾ as shown in table (2). The spectrophotometer reads absorbance mean (A) in nm, absorbance define as the amount of light absorbed by the material or body, but transmittance can define as the process in which light travels or crosses a body or surface without being absorbed or scattered^(5,6) and according to equation, transmittance percentage(T%) concluded from absorbance means.

Table(2): Chemical composition of artificial saliva medium⁽³⁾

Artificial saliva composition	Concentration (g/l)
NaCl	0.40
KCl	0.40
CaCl ₂ .2H ₂ O	0.795
NaH ₂ PO ₄ .2 H ₂ O	0.780
Na ₂ S ₉ H ₂ O	0.005
CO (NH ₂) ₂ (Urea)	1.0
Distilled water	1000

RESULTS

Statistical analysis include One Way Analysis of Variance (ANOVA) and Duncan Multiple Range tests at (P≤0.05) was performed to evaluate the statistical differences in the absorbance means among

tested composite resin, One Way Analysis of Variance demonstrated significant difference in the absorbance means for the optical light among tested composite resin after immersion in artificial saliva as shown in Tables (3,4).

Table(3): One Way Analysis of Variance(ANOVA) for the differences in absorbance mean among tested composite resin at the same immersion time.

		Sum of Square	Df*	Mean Sequare	F value	**P value
Between group	1,2,3 at G	2338	2	1.160	6.423	0.005
Within group		4.914	27	0.182		
Total	Zero time	1.252	29			
Between group	1,2,3 at 1day G	2477	2	1.238	4.227	0.025
Within group	Immersion time	7.91	27	0.293		
Total		10.38	29			
Between group	1,2,3 at 7 day G	277	2	1.389	5.783	0.008
Within group	Immersion time	6.482	27	0.240		
Total		9.259	29			
Between group	G1,2,3 at 28 day	2443	2	1.221	5.532	0.01
Within group	Immersion time	5.961	27	0.221		
Total		8.403	29			

*Df=degree of freedom , **P≤0.05 mean significant different exist.

Table (4): Duncan Multiple Range Tests for the Absorbance mean for the three different types of composite resin after storage in artificial saliva

TIME INTERVALES	TYPES OF COMPOSITE	MEAN ±SD	DUNCAN GROUP
Without immersion in artificial saliva	1. Els saremco	0.221±0.125	C
	2. Tetric	0.259±0.227	B
	3.Solitaire 2	0.831±0.694	A
After 1 day immersion in artificial saliva	1. Els saremco	0.302±0.244	C
	2 .Tetric	0.398± 0.314	B
	3. Solitaire 2	0.954±0.848	A
After 7 day immersion in artificial saliva	1.Els saremco	0.272±0.260	C
	2.Tetric	0.308±0.290	B
	3.Solitaire 2	0.935±0.752	A
After 28 day immersion in artificial saliva.	1.Els saremco	0.247 ± 0.222	C
	2.Tetric	0.291±0.271	B
	3. Solitaire 2	0.873±0.733	A

p-value ≤0.05, Different letters mean significant different exist

Results showed that at the same immersion time in artificial saliva media, Solitaire 2 composite resin had the highest

absorbance mean specially after 1day immersion in artificial saliva (0.954) nm followed by Tetric n ceram (0.398) nm, Els

Absorbance and transmittance for composite resins stored in artificial saliva

Saremco (0.302) nm after 7,28 day immersion in artificial saliva, there are slight increase in absorbance means for Solitaire2(0.935,0.873), Tetric(0.308,0.291), Els (0.272,0.247) in compared with zero time(before immersion in artificial saliva) Solitaire (0.831), Tetric (0.259), Els(0.221).

No significant differences in absorbance mean for each type of composite resin at different immersion time in artificial saliva as shown in Tables (5,6). Els extra showed the highest transmittance percentage followed by Tetric and Solitaire 2 composite resin as shown in table (7) Figure (2).

Table(5): One Way Analysis of Variance(ANOVA) for each type of composite resin at different immersion time in artificial saliva.

		Sum of Seq.	Df*	Mean Seq.	F value	**P value
Between group	G1	0.011	3	0.004	0.072	0.975
	Within group	1.869	36	0.052		
	Total	1.88	39			
Between group	G2	0.098	3	0.033	0.416	0.742
	Within group	2834	36	0.079		
	Total	2933	39			
Between group	G3	0.253	3	0.084	0.167	0.918
	Within group	18.23	36	0.506		
	Total	18.486	39			

*Df=degree of freedom , **P \geq 0.05 mean no significant different exist

Table(6): Duncan Multiple Range test for absorbance mean for different types of composite resin at different immersion time in artificial saliva.


TYPE OF COMPOSITE	TIME INTERVALS	MEAN \pm SD	DUNCAN GROUP
G1 Els	Without immersion	0.221 \pm 0.125	C
	After 1 day	0.302 \pm 0.244	C
	After 7 day	0.272 \pm 0.260	C
	After 28 day	0.247 \pm 0.222	C
G2 Tetric	Without immersion	0.259 \pm 0.227	B
	After 1 day	0.398 \pm 0.314	B
	After 7 day	0.308 \pm 0.290	B
	After 28 day	0.291 \pm 0.271	B
G3 Solitaire 2	Without immersion	0.831 \pm 0.694	A
	After 1 day	0.954 \pm 0.848	A
	After 7 day	0.935 \pm 0.752	A
	After 28 day	0.873 \pm 0.733	A

Same letters for each group mean no significant difference

Table (7): Transmittance values(T%) for three different types of composite resin at same immersion time.

Time intervals	Types of composite	Transmittance (T%)
Without immersion in arti. saliva	Els	60
	Tetric	56
	Solitaire 2	14.1
After 1 day immersion in art.saliva	Els	49.8
	Tetric	39.9
	Solitaire 2	11.1
After 7 day immersion in art.saliva	Els	53.4
	Tetric	49.2
	Solitair 2	11.6
After 28 day immersion in art. saliva.	Els	56.6
	Tetric	51.16
	Solitaire 2	13.3

Absorbance(A)=2-LogT%⁽²⁴⁾, T%=10^(2-A)

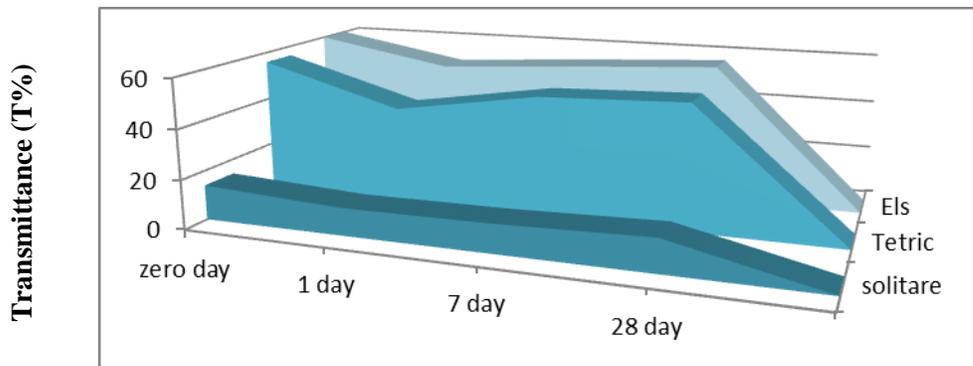

Figure(2): Histogram showing differences in transmittance percentage (T%) for different types of composite resin.

DISCUSSIONS

The search for direct restorative material combining excellent esthetic with superlative physical, mechanical and biological properties has driven researches to study various properties of different restorative materials⁽¹⁰⁾.

For a long time, dental professionals were satisfied with restorations that showed excellent shape and contour, good marginal adaptation considering color and optical properties of secondary importance. Possibly due to the limited knowledge of dental professionals about optical and physical properties, include absorbance and transmittance for the optical light^(10,11).

UV-Visible light spectrophotometer has been reported as an efficient method to verify the absorbance mean of the optical light for composite resin at wave length 245nm^(5,6, 10,11).

The best results were achieved with specimens of composite that received surface finishing and polishing which attributed to the removal of the surface layer of the resin rich inorganic matter which susceptible to staining, also the specimens thickness standardized less than 1mm because increasing the specimens thickness effect on result and lead to increase light absorbance and reduce its light transmittance^(5,6).

Several factors such as polymeric matrix, refraction index, type of monomer, filler

type and content can influence the light absorbance, transmittance and opacity of composite resins, these properties must be thoroughly evaluated in order to ensure esthetic longevity of a restoration^(12,13, 14,15). Optical properties of dental composite are not only vital for their effective in clinical used as esthetic restorative materials but also affect on their photo polymerization. composite composition, including choice of monomer filler and pigments effect on the matching of shade and transmittance between the final cured composite and adjacent natural teeth⁽⁷⁾.

Also optical properties of composite restorative both cured and uncured are important in a procedure of photo activation since they may affect light transmission and therefore materials conversion upon which effect on mechanical properties and ultimate clinical performance are dependent⁽⁷⁾. Statistical analysis shown significant difference in the absorbance means for the optical light among tested different types of composite resin at the same immersion time (zero,1,7,28) days in artificial saliva media, there are significant difference in the absorbance means at P value ≤ 0.05 for the optical light among tested composite resin after immersion in artificial saliva at the same immersion time as shown in Table (3,4). Solitaire 2 composite resin showed highest absorbance mean because the inclusion of poly glass in composite resin

reduce the amount of optical light transmittance increase the absorbance mean through the structure^(6,16,17) and this fact agree with result of this study, specially after 1day immersion in artificial saliva (0.954) nm followed by Tetric (0.398) nm, Els extra (0.302) nm. After (7,28) day immersion there are slight increase in absorbance means for Solitaire 2 (0.935,0.873), Tetric (0.308,0.291), Els (0.272,0.247) in compare with zero time (before immersion) Solitaire 2 (0.831), Tetric n ceram (0.259), Els (0.221), as a result of storage in artificial saliva water sorption, stain, gain and loss in the weight of composite resin bars, changing in absorbance mean for optical light without significant differences during different immersion time, no significant differences in absorbance mean for each type of composite resin at different immersion time in artificial saliva as shown in Table (5,6).

Transmittance is a propriety of substance that permit the passage of the light through the structure^(4,14,15),the transmittance of dental composite depend on their scattering and absorption coefficients of the resin, filler particles, pigment⁽⁴⁾. Thus the inherent transmittance of the material may contribute to matching the shade of the underlining tooth and the tooth adjacent to it⁽⁴⁾. There are many variables that may affect the transmittance of the material including polymerization shrinkage, saliva aging, filler particle composition and size^(4,11).

Els extra composite resin, microhybrid showed the highest transmittance percentage as compared to other experimented composite resin at different immersion times in artificial saliva as shown in Table (7), Figure (1). This can be explained by fact that microhybrid particles resin are more transmittance than nano and poly glass hybrid composite resins and this agree with result of the study^(16,17). Tetric n-ceram resin nanohybrid shows more transmittance percentage than Solitaire 2 poly glass hybrid composite resin. According to Santos *etal*⁽¹²⁾ study, nano composites resin showed a higher gain in transmittance at a fixed thickness than poly glass hybrid resins, which attributed to the filler particle size and distribution of nano composite and this agree with result of this study. Therefore, filler particles size and content significantly affected the light transmittance characteristics and color of composite resin⁽¹²⁾.

Nakamura *etal*⁽¹⁸⁾ found that transmittance was not modified over time, in contrast, lambre *etal*⁽¹⁹⁾ reported that transmittance diminished gradually over time with the longest immersion time leading to the lowest transmittance value. Lee *etal*⁽²⁰⁾ examined how transmittance is affected by storage in salivary enzyme versus a phosphate buffered saline solution for 9 week ,they concluded that transmittance value tend to decrease after 9weeks storage in solution, this is

important because the results show that enzymes of saliva probably has little effect on transmittance of composite. Lea and lee⁽²¹⁾ conclude that transmittance parameter tend to varying according to individual brand of composite resin. Some authors state that the transmittance decrease with aging and this should be taken in consideration during shade selection of resin composite, absorbance means not effect on degree of radio opacity of composite resin⁽²²⁾. The incorporation of inorganic nano particales into polymer matrix can significantly influence the properties of the matrix and the obtained composite might exhibit improved thermal, mechanical and optical properties, the properties of polymer composite depend on the type of incorporated nano particals, their size, shape and interactions with the polymer matrix, the tensile strength and elongation decrease with increasing cerium oxide(CeO₂) nano particales composite resin up to 3.0 wt%. also the UV absorption properties was noticeable improved⁽²³⁾.

CONCLUSIONS

From results of this study we concluded that Els microhybrid composite resin less absorbance and high transmittance for the optical light from the Tetric n ceram nanohybrid composite resin, Solitare 2 poly glass composite resin showed more absorbance values with highest significant differences and with reduced amount of light transmittance compared to

other experimented composite resin, also the absorbance of the experimented groups was similar no significant differences in terms of different immersion time in artificial saliva.

REFERENCES

1. Senawonges P, Pongorueks AP. Surface roughness of nanofill and nanohybrid resin composite after polishing and brushing. *J Esthe Resto Dent.* 2007;19:265-275.
2. Powers JM, Sakaguchi RL. Restorative dental materials. 12th ed. St. Louis. Mosby. 2006; P: 40-42.
3. Preetha A, Banje A. Comparison of artificial saliva substrate. *Trends Bio mater Art Organ.* 2005;18(2):13 -22.
4. Lee YK. Influence of filler on the difference between transmitted and reflected colors of experimental resin composite. *Dent Mater J.* 2008 ;24(9):1243-1247.
5. Costa SX, Becker AB, Souza O. Effect of four bleaching regimens on color changes and micro hardness for dental composite nano fill. *Int J of Dentistry.* 2009; 31(2):48-55.
6. Queiroz RS, Lima JP, Malta DA. Changes on transmittance mode of different composite resins. *J Materials Research.* 2009; 12(2): 127-132.
7. Howard B, Willson N, Newman S: Relation ships between conversion, temperature and optical properties during composite photo polymerization. *Acta Bio meter J.* 2010; 6(6):2053-2059.

8. Iatsuo E, Werne J, Finer N. Surface texture and roughness of polished nano fill nanohybrid resin. *Dent Mater J.* 2010; 29(2): 213- 223.
9. Hatim NA, Taqaa AA. Evaluation of the effect of curing – technique on color property for acrylic resin. *Rafiq Dent J.* 2004; 8(1): 28 -33.
10. Masti A, Onofrio AB, Conceicao EN, Spolr AN. UV –Visible spectrophotometer direct transmittance analysis of composite resins. *Dent Mater J.* 2007; 23(6): 724-730.
11. Emani N, Jodahl, Soderhrh I. How filler properties filler fraction sample thickness and high source affect light attenuation in practical filled resin composite. *Dental Mater J.* 2013; 21(8): 721 -730 .
12. Santos GB, Monte A, Silva EM. light transmission on dental resin composite. *Dent Mater J.* 2008; 24 (5): 571-576.
13. Buchalla W, Attint T, Hilger RD. The effect of water storage and light expose on the color and translucency on hybrid and microfilled composite. *prosth Dent J.* 2002; 87(3): 264-270 .
14. Luce MS, Compbell CE. Stain potential of four microfill composite . *prosth Dent J.* 1998; 60(2): 151 -154.
15. Iazzety G, Burgess JO, Gardinr D, Ripps A. Color stability of fluorid contains restoration material. *Oper Dent J.* 2000; 25 (6):520-525.
16. Eldiwany M, Friedl O, powers JM. Color stability of light cured and post cured composite. *Am J of Dent.* 2000; 8(4): 179 - 181.
17. Sampath R, Raama GS. Effect of glass fibers on light transmittance and color of fiber reinforced composite. *Dent Mat J.* 2008; (1): 34-38.
18. Nakamura T, Saito O, Mizuno M, Tanaka M. Changes in translucency and color of particular filler composite resin. *Int Prosth J.* 2002; 15(5): 494-499.
19. Lamber P, Amey C, Vanherle G. aesthetic limits of light cured composite resin in anterior teeth. *J Prost Dent.* 2000; 40(5): 149-158.
20. Lee Y, Kim S, Powers J. Changes in translucency of resin composites after storage in salivary esterase. *Dent J Esthet Restor* 2005;17(5): 293-9.
21. Lea SH, lee YK. Effect of thermocycling on optical parameter of resin composite. *Am J Dent.* 2008; 22(7): 653-60.
22. Lee YK, Lu H, Powers JM. Changes in opalescence and fluorescence properties of resin composites after accelerated aging. *Dent Mater J.* 2012; 22(7): 653-60.
23. Dao N, Lull M, Nguen QK. UV absorption by cerium oxide nano particales / epoxy composite thin film. *Adv Nat Sci NanoSci Nano Tech.* 2011; 2(4):188-193.
24. Skooge DA, West DM, Holler F. Fundamental of Analytical Chemistry. 8thed. Western European. 2013. Chapter24; P: 657-659.